

Kunststoffe international

SPECIAL

Variotherm Temperature Control

page 16

INJECTION MOLDING


Integration of Composite Films
Lighting and Control Sensors in
Decorative Surfaces

page 39

SPECIAL

Lightweight
Construction

page 27

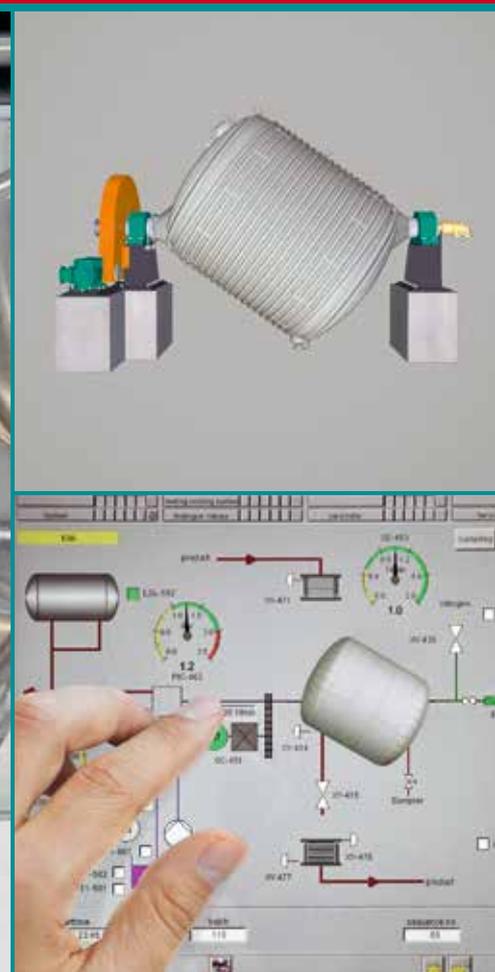

www.sp-prottec.com

**ProTec Polymer
Processing GmbH**

Calcium Carbonate Improves Blown Film Properties

Direct Extrusion with Mineral Fillers

The addition of calcium carbonate into the blown film process is the most effective way to boost productivity and output, and to improve the mechanical properties of the film. Thanks to a newly developed technology, direct dosing of CaCO_3 powder is now possible.

Evolution 3-layer Ultra Fusion Line producing yellow/black film with high amount of CaCO_3 powder for soil packing bags (figure: Reifenhäuser)



State-of-the-art blown film extrusion lines can process the most diverse raw materials: polyolefins, barrier and tie resins, as well as various additives, masterbatches and bio polymers. Generally, all these resins are available as pellets, produced within the reactor or compounded with additives in a second step before they are delivered to the converters. Film producers combine these resins, additives and masterbatches to produce miscellaneous blown films of up to 11 layers. Mineral modifiers offer the opportunity for more economic film production. At the same time mechanical properties of polyolefin films are improved which enables significant down-gauging. Here cal-

cium carbonate (CaCO_3) represents the most popular mineral modifier.

Usually, CaCO_3 is added to polyolefins in form of masterbatches. However, some specific production lines allow direct dosing of CaCO_3 powder into pipes and polypropylene sheets.

With the Evolution Ultra Fusion Technology recently developed by Reifenhäuser Blown Film GmbH, Worms, Germany, it is now possible to directly add CaCO_3 powder to a blown film converting line. These lines working with the Ultra Fusion Technology are equipped with a special co-rotating twin-screw extruder, REtruder type (Fig. 1), and are designed as mono – or more advantageously – as

3-layer lines with two standard extruders for thin skin layers (Title figure).

A high-precision powder dosing system and the adapted mixing screw elements in the REtruder ensure the optimum filler distribution in the polymer melt (Fig. 2). Furthermore, an efficient vacuum degassing system is used for the removal of moisture in the raw material.

CaCO₃: a Natural Product

CaCO_3 represents the most significant mineral within the plastics industry and is unequivocally the most consumed, as it is used in numerous applications. From the most simple to the most demanding ap-

plications, CaCO₃ can be added to a variety of polymers, ranging from polyolefins to PVC, together with biopolymers, polystyrenes and polyurethanes.

CaCO₃ is a mineral frequently found as around 4% of the continental earth crust consists of it, for example in the form of chalk, limestone and marble. Rocks are extracted at a quarry and transformed into powder by milling, are strained and surface-treated. After these steps it is ready for its numerous uses in plastics applications. Due to the large number of CaCO₃ deposits, this mineral can be considered as a virtually inexhaustible raw material source.

It must be noted, however, that the selection of the right CaCO₃ powder type, i.e., the right specific particle size distribution, high purity and optimized surface treatment, is a prerequisite to obtain an outstanding performance in plastics applications.

Why Is CaCO₃ Used in Blown Film?

Apart from anti-blocking properties, calcium carbonate offers a wide variety of performances contributions, such as higher mechanical values and enhanced optical properties, or other specific features that are always combined with a high cost savings potential.

In addition, it modifies the physical properties within the polymer melt. Compared to unfilled polyolefins CaCO₃ has a substantially higher density, thermal conductivity and lower heat capacity and it remains in solid form during the extrusion process. Hence, the main features resulting from this are:

- Increase of the extruder output,



Fig. 1. REItruder (special co-rotating twin-screw extruder) installed in an Evolution 3-layer Blown Film Line (figure: Reifenhäuser)

- reduction of the melt pressure and extruder torque,
- more efficient and as a result faster cooling of the film bubble,
- melt homogenization effect.

Summarizing, the addition of CaCO₃ in a blown film line is a simple and efficient way to increase productivity and output rates.

Improved Film Properties

The addition of fine and surface-treated CaCO₃ into a semi-crystalline polymer matrix modifies the properties of a blown film, such as:

- Increase of stiffness,
- higher dart drop impact resistance,
- anti-blocking effect,
- higher tear propagation resistance (Elmendorf),
- improved barrier properties,
- slight increase in surface tension,
- non-stretched: rise of film density,
- stretched: reduction of the density and if desired with a permeation function.

The magnitude of the above mentioned changes in polymer properties strongly depends on the film formulation, film thickness, the mineral content, but also on the CaCO₃ type.

Prominent examples of blown film applications where CaCO₃ is successfully added include shopping bags, t-shirt bags, garbage bags, paper-like films, agricultural films, heavy-duty bags, and backsheet films.

Lower Formulation Cost

As the addition of CaCO₃ increases the film density, it is necessary to reduce the film thickness in order to keep a constant film weight, the so-called down-gauging. It must be noted that this increase is not in linear correlation with the mineral content. For example, with 30% CaCO₃ content, the required down-gauging will "only" be at a level of 20% to keep the film weight constant.

Increased Sustainability

Over the whole process chain there are additional energy savings. The Ultra Fusion Technology provides higher sustainability by admixing CaCO₃ powders. The process saves heat energy during extrusion, because these minerals have significant lower specific heat than polymers. From this results a smaller product carbon footprint and a significantly reduced environmental impact.

Advantages of Direct Dosage

The direct dosage of CaCO₃ allows substantial savings in raw material costs. The cost saving potential is »

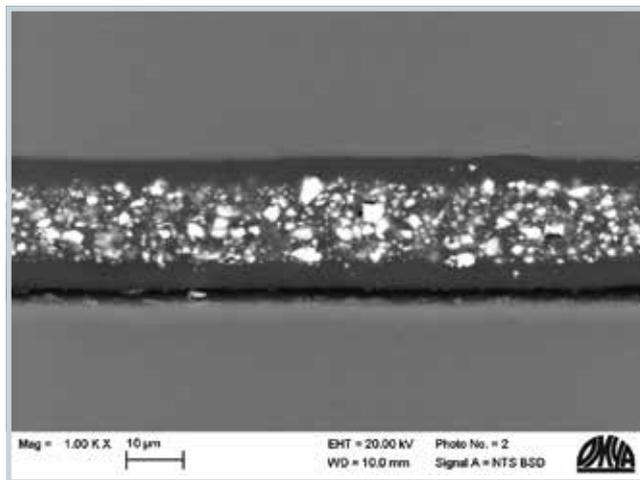


Fig. 2. SEM of blown film produced with the Ultra Fusion Technology and containing 35% of CaCO₃ (in this case with Omyafil 707-AV from Omya International AG, Oftringen, Switzerland) in the middle layer (figure: Omya)

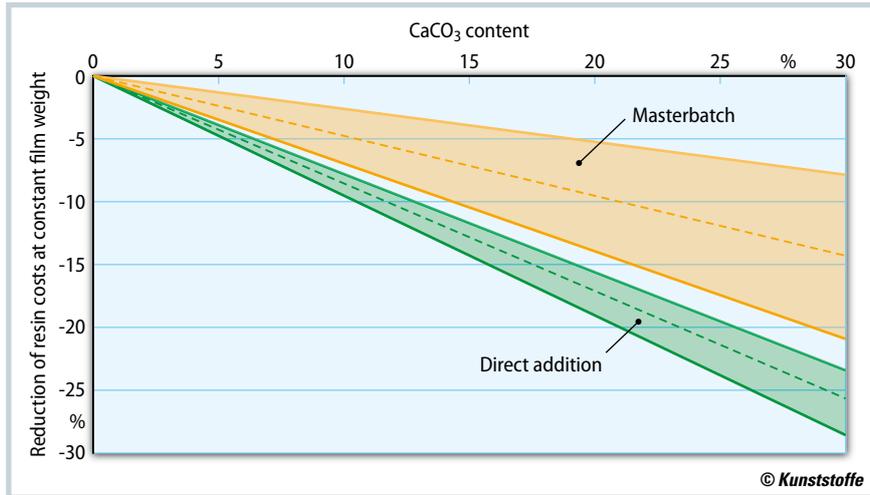


Fig. 3. Estimation of cost saving potential by adding CaCO₃ in blown film by keeping the film weight constant (for further information, please read the paragraph 4) (figure: Reifenhäuser)

clearly illustrated in **Figure 3**. A polymer price of approximately 1,100 EUR/t was taken as a basis.

In the orange area the figure shows the savings potential by using a masterbatch with regard to a masterbatch price between 550 and 900 EUR/t.

The figure also illustrates, in green, the additional savings potential on material cost by using directly CaCO₃ powder via direct extrusion by using the Evolution Ultra Fusion Technology. This technology is very profitable, especially when

the filler level needs to be high and the extrusion line output is of importance.

A further advantage of a direct extrusion solution is the opportunity to add directly other minerals such as TiO₂, making cost savings perhaps even more significant.

Also in cases where down-gauging is technically not feasible, direct extrusion of CaCO₃ will nevertheless offer potential cost savings together with improved mechanical properties through the reinforcement effect of the mineral.

The Author

Grad.-Eng. Ralf Wiechmann is Product Manager Blown Film Lines at Reifenhäuser Blown Film GmbH, Worms, Germany.

Service

Digital Version

➤ A PDF file of the article can be found at www.kunststoffe-international.com/963033

German Version

➤ Read the German version of the article in our magazine *Kunststoffe* or at www.kunststoffe.de

Conclusion

The Evolution Ultra Fusion Technology offers the opportunity to successfully incorporate high amounts of CaCO₃ powder into blown films. This leads to significant cost savings due to the substitution of more expensive polymer resins. The positive effect of CaCO₃ on film properties enables significant film down-gauging, and in addition, the product carbon footprint of the film can be reduced. ■